



ITT

Robert Egerman

(Presented by Michael Melocchi, Ph.D.)

robert.egerman@itt.com

Low-weight, Low-cost, Low-cycle Time, Replicated Glass Mirrors

This document is subject to the controls of the Export Administration Regulations (EAR) and has been classified as EAR99 under U.S. Export Control laws and regulations. The recipient is responsible for ensuring compliance to all applicable U.S. Export Control laws and regulations.

Engineered for life

0.5m f/1.95 Replicated Corrugated Borosilicate Mirrors

*ITT Geospatial Systems
Rochester, NY*

INNOVATION


Development of technology to rapidly (< 1 month) fabricate large high quality , low mass, optics utilizing high temperature forming and replication processes

ACCOMPLISHMENTS

- ◆ Finished 0.5m mounted plano part to 52 nm-rms (ITT IR&D)
- ◆ Designed 0.5m borosilicate mirror blank and tooling for on-axis parabola
- ◆ Conceptual design for mirror mounts for mirrors
- ◆ Fabricated 7 0.5m f/1.95 corrugated mirror blanks matching ROC < 0.3%
- ◆ Polishing has been performed on two of blanks
- ◆ One part finished to a level that is within capture range of ITT's ion figuring processes

COMMERCIALIZATION

- ◆ ITT Corrugated Mirrors
- ◆ U.S. Patent #: 7,429,114 B2
- ◆ Commercial application opportunities are currently being explored
- ◆ Product is not yet available for purchase as a commercial item

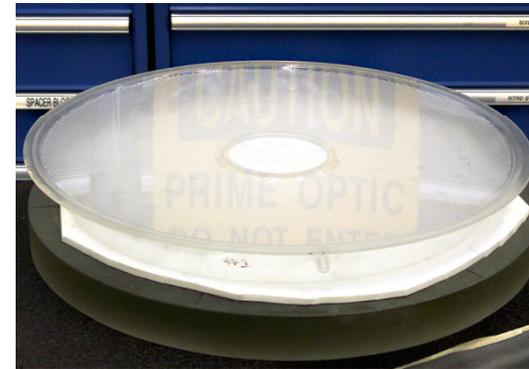

0.5m ACT Corrugated Mirror Blank With Center-hole

GOVERNMENT/SCIENCE APPLICATIONS


- ◆ Use in ground and space based optical systems
- ◆ Plano IR&D mirror needs additional testing to raise Technology Readiness Level (TRL) to 6 for flight applications
- ◆ Parabolic part TRL needs advancement to TRL 6 though incorporation of mount design and qualification testing
- ◆ For some earth science LIDAR applications, technology needs to be scaled to larger sizes and hexagonal geometry
- ◆ Future technology development opportunities include elimination of need for any conventional grinding processes and extending to other materials such as Corning ULE®

Agenda

- Introduction
- Corrugated Mirror Description
- Key Demonstrations of Corrugated Mirror Technology
 - Plano mirror prototype
 - Plano 0.5 m diameter mirror
 - Spherical 0.5 m diameter mirror
 - Parabolic 0.5 m diameter mirror with center-hole
- Technology development opportunities
- Summary

Introduction

- ITT is developing a family of mirror designs and processes to enable the fabrication of high quality lightweight mirrors which can be delivered for a fraction of the time and cost of more traditional mirrors
- One of the mirror types in this family is called a “Corrugated Mirror”
- Technology goals for this mirror type:
 - Size: up to 2 m
 - Areal density: 5-10 kg/m²
 - Materials: borosilicate, ULE[®], other glasses
 - Figure: 50 nm RMS
 - Fabrication time: 1 week blank fabrication
3 weeks optical finish

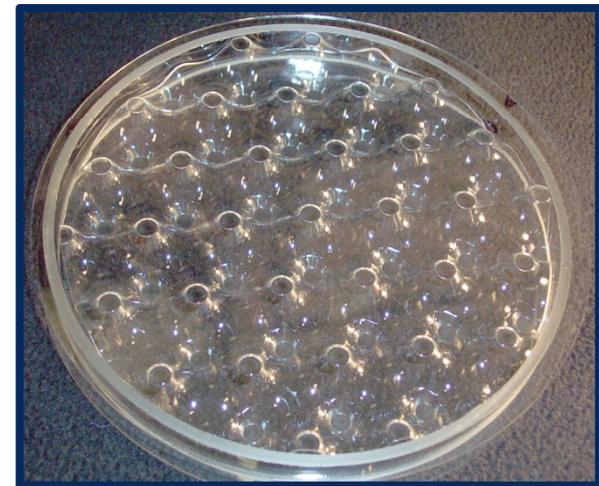

Prototype Corrugated Mirror

Introduction (continued)


- ITT has completed several key demonstrations of Corrugated Mirror technology and is actively working others
- Development has progressed through several key gates as demonstrated by:
 - I. Plano mirror early prototypes (< 0.3 m)
 - II. Plano mirror 0.5 m diameter (optically finished and mounted)
 - III. Spherical mirror 0.5 m diameter mirror blanks (technology extended to curved surfaces)
 - IV. Parabolic mirror 0.5 m with center-hole (currently in optical finishing)

This presentation summarizes ITT's key demonstrations to date of Corrugated Mirror Technology



Corrugated Mirror Description


- Corrugated glass mirrors are closed-back lightweight optics
- Key features include:
 - Mirror components are molded from flat glass sheets and fused together at high temperature
 - The optical surface is formed over a precision mandrel
 - Mirror has depth resulting in excellent global stiffness-to-weight
 - Stiff lightweight optical facesheet
 - Facesheet itself has 3 layer 'sandwich' construction which results in 60%-70% mass reduction while maintaining local stiffness

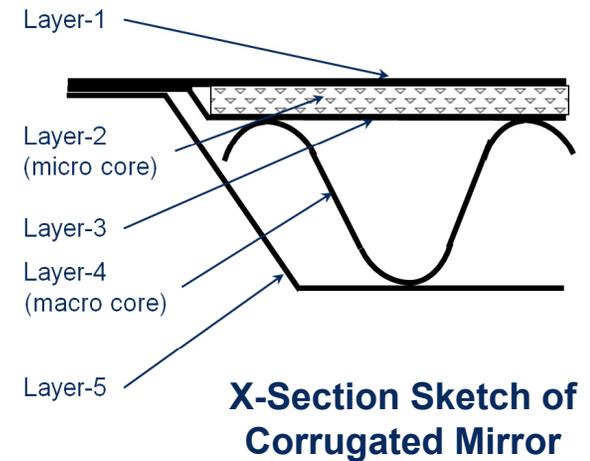

Corrugated Mirror Description (continued)


- A Corrugated mirror can be fabricated for a fraction of the time and cost of more traditional mirrors
 - All mirror components discussed in this briefing are currently fabricated from COTS material (Schott Borofloat® sheet material)
 - Borofloat® has low cost due to high volume from flat panel display market
 - Schott has demonstrated ability to fabricate sheets 0.7 mm thick in sizes up to 2.3m x 2.3m
 - Replication enables conventional mirror finishing processes to be minimized/eliminated

Corrugated borosilicate mirrors have rapid low-cost fabrication due molding and replication processes as well as the COTS glass sheet material

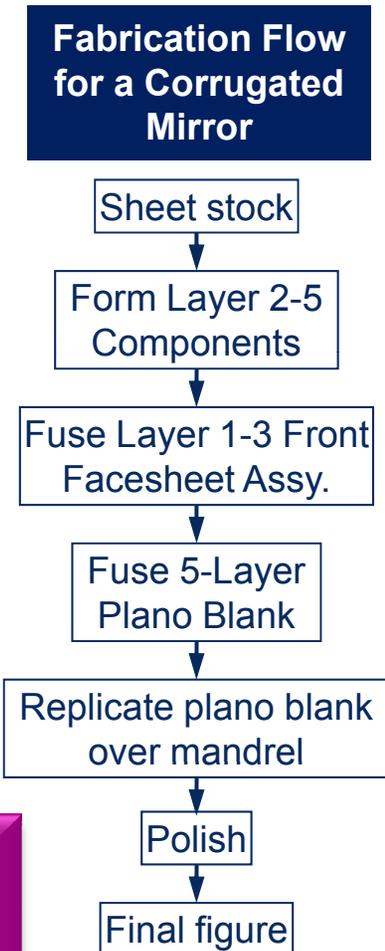


Lightweight Front Facesheet Fabrication

- The front facesheet consists of 3 layers fused together in a lightweight and stiff sandwich arrangement
 - Layers 2 & 3 are molded independently and then fused with layer-1
 - This facesheet reduces mass while maintaining local plate stiffness


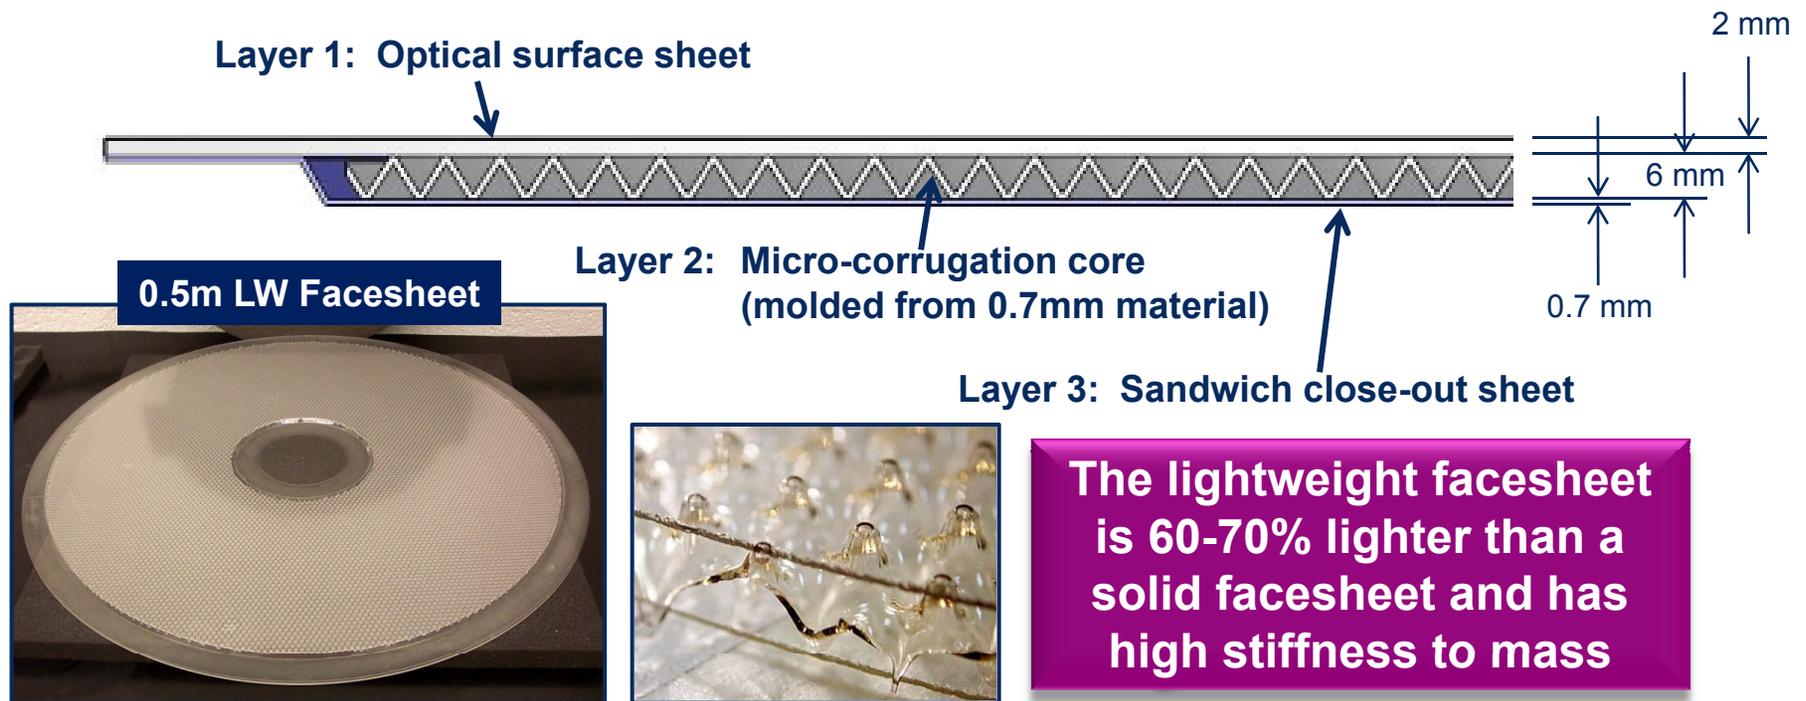


Corrugated 0.5m Mirror Fabrication (5 layer)

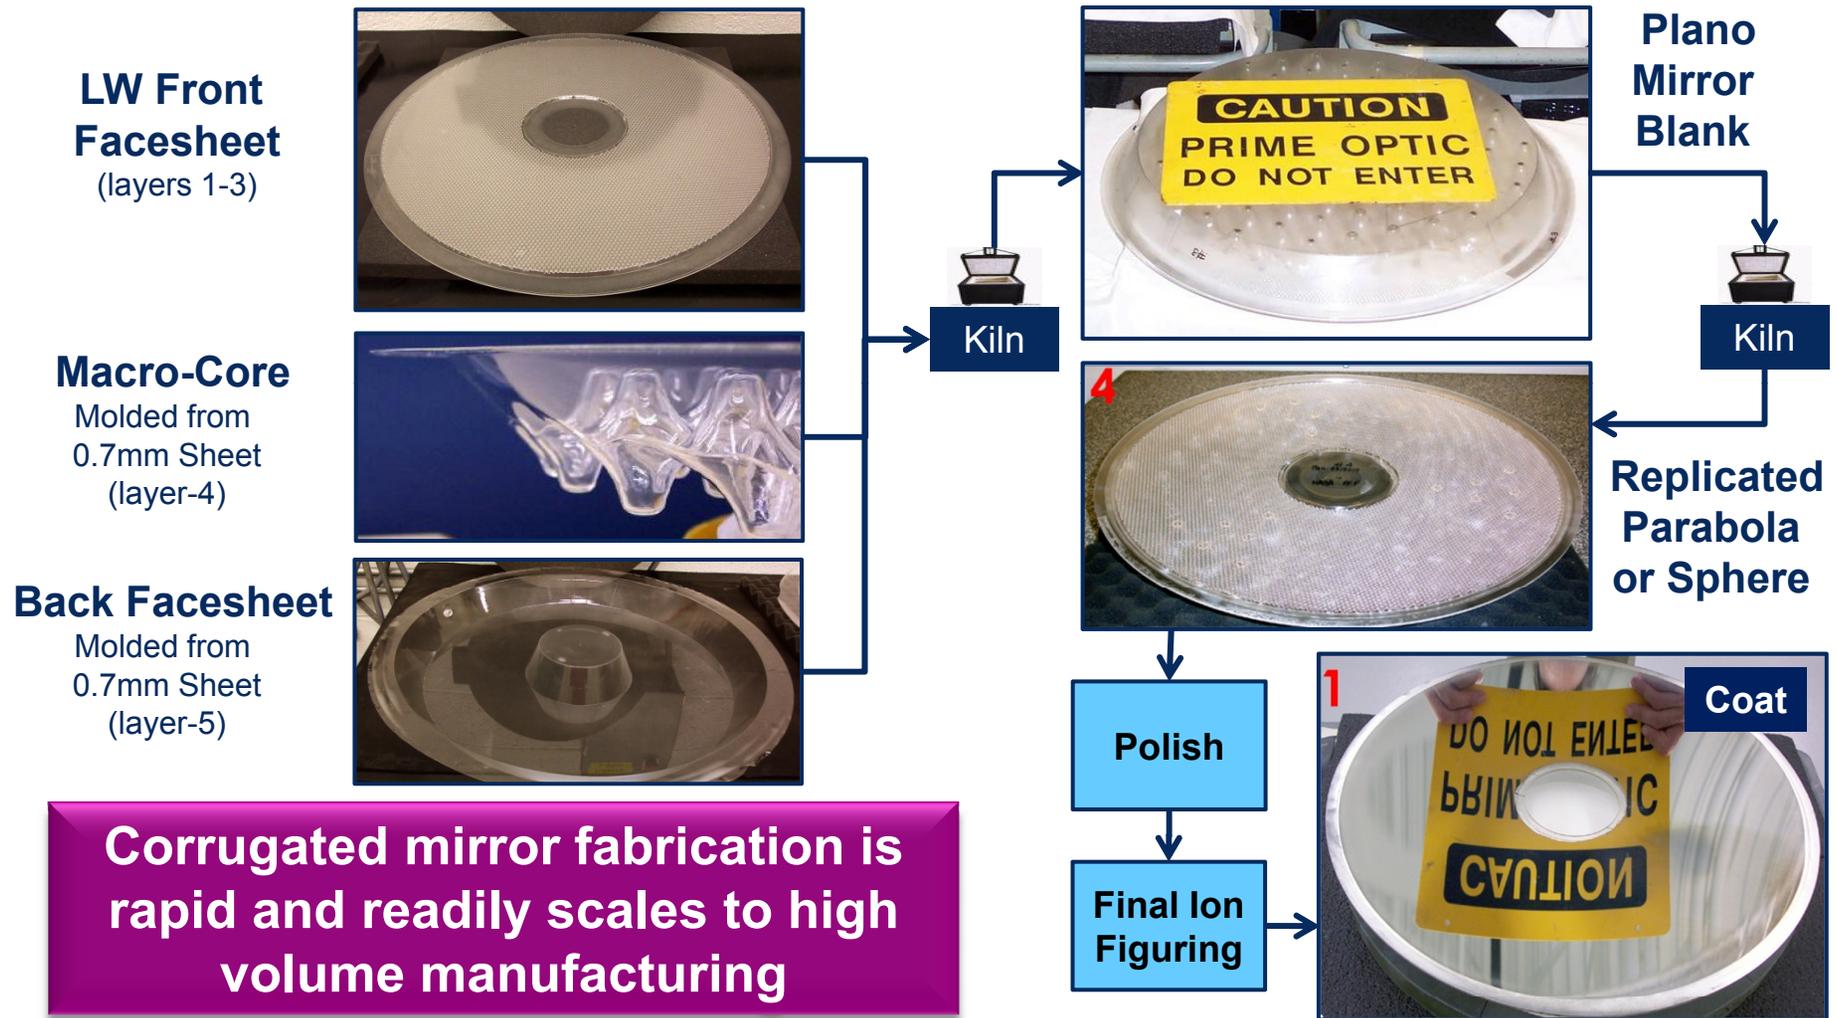


I. Early Prototype Plano Mirrors

- Early prototype mirrors had a 3 layer design (i.e. no lightweight facesheet)
 - Fabrication time: 5 days
 - Optical figure: 60 nm RMS surface
 - Areal density/size: 10 kg/m² / 150mm Ø
 - Accuracy of molded surface: ± 2 μ m

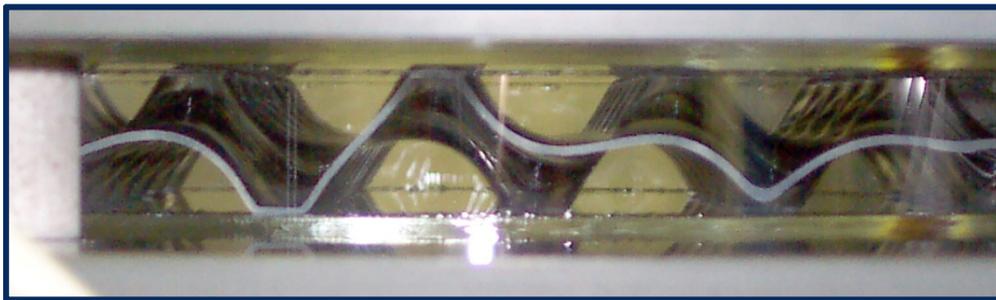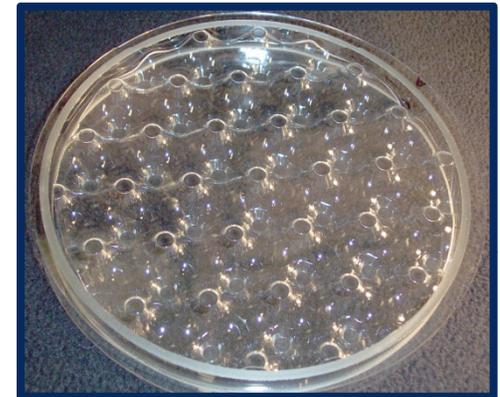

3-layer prototypes validated rapid fabrication approach for lightweight corrugated mirrors

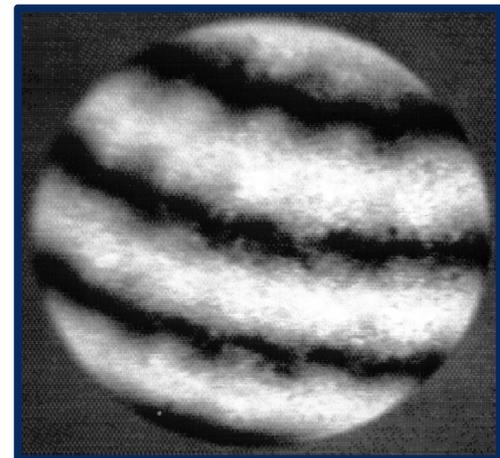

II. Plano 0.5m Mirror, Finished & Mounted

ITT fabricated several 0.5m blanks

Areal Density: ~11 Kg/m²

5-layer design provides significant global and local mirror stiffness compared to 3-layer design



Top 3 layers are a micro corrugation

6 mm tall micro core

Top 3-layers function as front facesheet


Top layer currently 2 mm to allow for fine grind prior to polish



Environmental Testing


Testing performed by NASA GSFC under Innovative Partnerships Program funding

Survived 7-g RMS axial vibrate (~32-g peak)

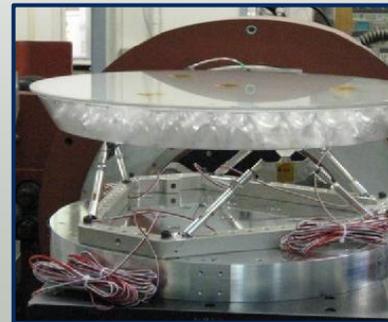

Mounted Plano Mirror Finishing


Part without center-hole mounted and finished to 52 nm RMS

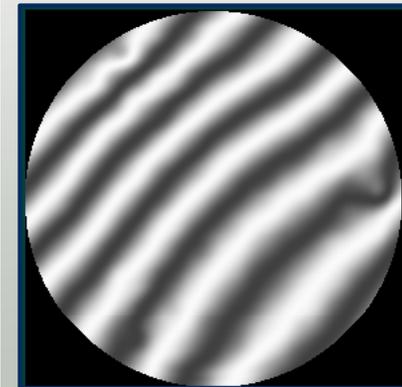

Fabrication processes were successfully scaled up from 0.15m to 0.5m planos plus design was matured to include a stiffened facesheet and mounts

III. Spherical 0.5m Mirror Blanks

- ITT fabricated three f/2 spherical mirror blanks
- Blanks were fabricated to demonstrate extension of fabrication processes to spheres and aspheres

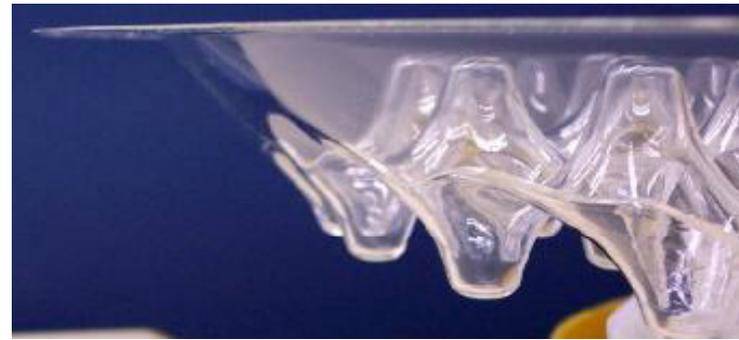

Macro Core




0.5m dia f/2 Spherical Mirror Blank

Fabrication processes were extended to produce spherical surfaces. This extension successfully paved the road for subsequent fabrication of aspheres.

IV. Parabolic 0.5m Mirror


- Activity funded by ESTO ACT grant
- Program goals
 - Design and fabricate a 0.5m f/1.95 parabola, <math><15 \text{ kg/m}^2</math> mounted
 - Develop conceptual design of mounts for Taurus launch
 - Mirror to include a center-hole
 - Figure <math>< 100\text{nm}</math> RMS surface
- Status
 - Multiple mirror blanks successfully completed (7 blanks in <math>< 9</math> weeks, furnace limited)
 - Blanks radius matched to 0.3%

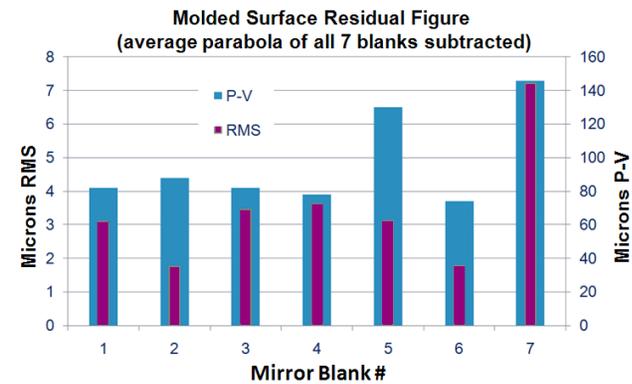


Rapid fabrication of multiple lightweight mirror blanks has been demonstrated

IV. Parabolic 0.5m Mirror (continued)

- Status (continued)
 - Two mirrors are in optical finishing
 - Mirror #1 current figure (pre-ion)
365 nm RMS (as of 6/1/10)
 - Mirror #2 being used to demonstrate computer controlled small tool polishing techniques
 - Finishing is progressing towards target figure as planned

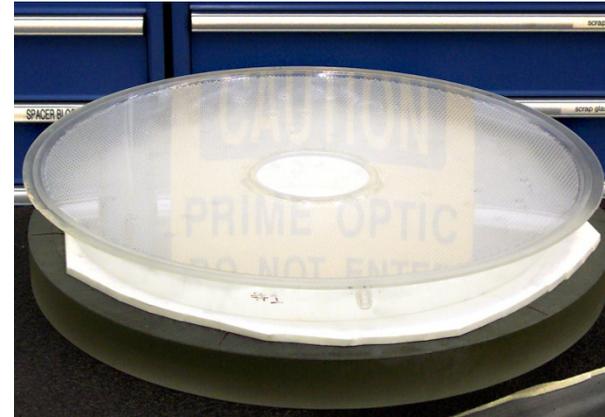

f/1.95 Parabolic Corrugated Mirror

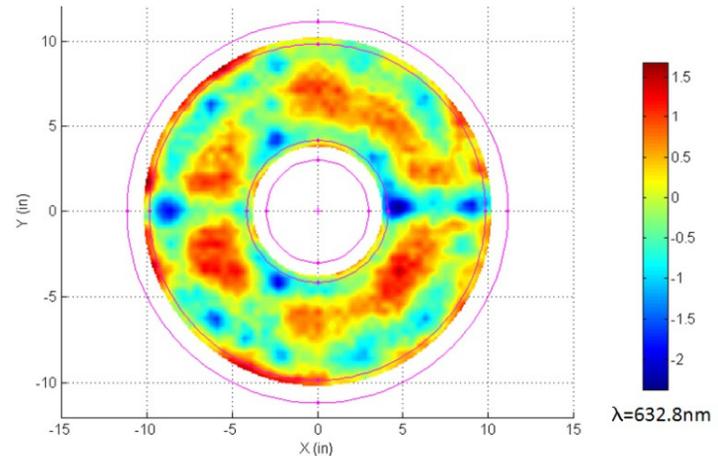

Surface Map of ACT Mirror # 1
prior to Ion (~365 nm RMS)

Finishing of LW parabolic mirrors with center-holes is another significant milestone in the advancement of Corrugated Mirror Technology

Technology Development Opportunities

- LW Mirror mounts for corrugated mirrors
- Qualification testing of mounted corrugated mirrors
- Scale to other sizes & shapes for different applications
- Replicate optical surface to tighter tolerance
 - Would reduce schedule & cost by eliminating current need for fine grind prior to polish
 - Would reduce areal density 2-3 kg/m² by allowing use of thinner material for the optical surface (layer-1)
- Extend corrugated mirror technology to other materials such as ULE[®] glass

Summary

ITT has developed and is successfully demonstrating designs and key processes which advance Corrugated Mirror Technology towards rapid fabrication of high quality lightweight optics at lower cost

Acknowledgements:

Dave Content, NASA's Goddard Space Flight Center

Sandra Irish, NASA's Goddard Space Flight Center

Parminder Ghuman, NASA's Earth Science Technology Office

Steven De Smitt & David Strafford, ITT Geospatial Systems

